


# TOOLING ALLOYS

## DATA SHEET Z-TUFF PM

ZAPP IS CERTIFIED TO ISO 9001

# ZAPP

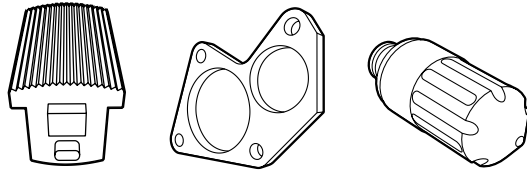

### CHEMICAL COMPOSITION

Carbon	0.7 %
Chromium	7.5 %
Vanadium	1.0 %
Molybdenum	2.0 %
Nickel	1.5 %

### DESCRIPTION

Z-Tuff PM is a powder metallurgy tool steel designed with toughness as the primary criteria. Its attributes include:

- \_ High impact strength and resistance to fracture while retaining exceptional compressive strength
- \_ Good wear resistance
- \_ Attainable hardness approaching HRC 62
- \_ Easily heat treated using common tool steel cycles
- \_ Consistency and reliability inherent with PM tool steel
- \_ thermo-shock resistant

This unique combination of properties makes Z-Tuff the choice in difficult applications involving high mechanical loads and risk of failure due to chipping and fracture. It offers a distinct advantage over standard air hardening grades in terms of toughness. At the same time it is clearly superior to the S series grades in terms of compressive strength and wear performance. It is a deep hardening grade that will maintain a high degree of dimensional stability, and a highly effective substrate for a variety of common tool coatings and surface treatments.



### TYPICAL APPLICATIONS

- \_ general tool and die
- \_ stamping, forming and fine blanking
- \_ punches
- \_ powder compaction

### PHYSICAL PROPERTIES


Modulus of elasticity E [GPa]	207
Density [g/cm <sup>3</sup> ]	7.66
Coefficient of thermal expansion over a temperature range of 20 - 540 °C [mm/mm/°C]	11.5 x 10 <sup>-6</sup>
Thermal conductivity [W/(m*K)]	24.2

### POWDER METALLURGICAL AND CONVENTIONAL MICROSTRUCTURE



The uniform distribution of carbides in the powder- metallurgical structure compared to conventional tool steels with big carbides and carbide clusters.

### TOUGHNESS

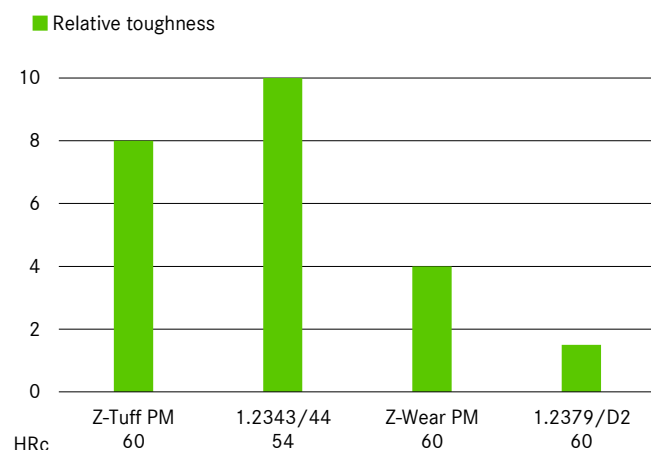

## THERMAL TREATMENTS

### SOFT ANNEALING

The material is heated uniformly to a temperature of 860-870 °C and then maintained at this temperature for 2 hours. Then, the material is cooled to 540 °C in a furnace at a cooling rate of maximum 15 °C per hour. It is then further cooled in still air down to room temperature. The typical hardness achieved by soft annealing is approximately 225-250 HB.

### STRESS RELIEVING (SOFT)

Rough machined material is stress relieved by heating to 600-700 °C. Once complete heat penetration has been reached (minimum 2 hours), the material is allowed to cool in the furnace to approximately 500 °C followed by cooling in air.

Hardened material is stress relieved at 15-30°C for 2 hours below last tempering temperature followed by cooling in air.

### STRAIGHTENING

Straightening should be done in the temperature range of 200-430 °C.

### HARDENING

Vacuum, salt, or protective atmosphere methods are generally used. Care must be taken to prevent decarburization.

### HARDENING

Hardening of Z-Tuff PM usually involves the use of two preheating steps according to the table on the right. Depending on furnace and charging, additional preheating steps can be implemented. In order to achieve a corresponding degree of dissolution of the alloying elements, as well as an appropriate hardening, minimum heat penetration times as given in the table are recommended. These holding times should be correspondingly adapted for thick or thin-walled material cross sections.


### QUENCHING

Quenching can take place in hot bath at 540°C, oil or pressurized gas. Quenching in salt bath or oil leads to maximum hardness, whereas cooling in vacuum can lead to lower values of 1-2 HRc. By use of vacuum quenching a minimum pressure of 6 bar is recommended. The appropriate pressure needs to be adjusted for complex tool shapes in order to minimize risk of cracking and tool distortion. For attaining ideal toughness properties, it is recommended to apply the hot bath quenching method. For attaining maximum hardness after quenching the cooling rate between 1000°C and 700°C needs to be maximized in order to minimize distortion in larger section sizes.

## TEMPERING

Tempering should be carried out immediately after the material has cooled down to below 40 °C or when the tool can be held with hands. Triple tempering with a holding time of 2 hours in each stage at the tempering temperature is necessary. It is important to ensure that the tools are cooled down to room temperature between the individual tempering stages.

### TEMPERING DIAGRAM

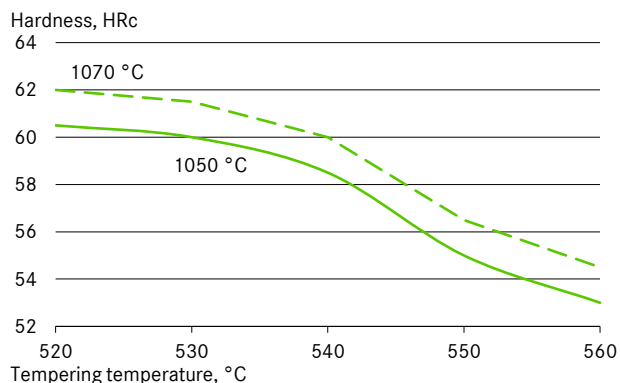

### HEAT TREATMENT INSTRUCTIONS

1st preheating	450-500°C
2nd preheating	850-900 °C
Hardening	as specified in table
Tempering	3 x each 2 hours as specified in table

Preferred quench method is high pressure inert gas (minimum 4 bar) or molten salt at 1025 °F.

Required hardness HRc ± 1	Austenit- izing soak temp [°C]	Austenit- izing soak time [min]*	Tempering tempera- ture[°C]**
59	1050	30	540
60	1050	30	530
61	1050	30	520
62	1070	20	530

\* Process variation and part section size can affect results. Soak times should be based on actual part temperatures. Use of load thermocouples is highly recommended during batch processing.

\*\*An increase in tempering temperature by 15°C can be used to reduce hardness 1 to 2 points HRc.

## SURFACE TREATMENT

This grade is an excellent substrate material for use with the various commercially available PVD coating processes. Conventional nitriding and steam tempering can also be used. Coating vendors should be consulted to select the optimum process for a given application. Care must be exercised during CVD and other surface treatment processes that can alter the original heat treatment of the tool.

## MACHINING DATA

### TURNING

Cutting parameter	Turning with cemented carbide		HSS
	medium turning	finish turning	
Cutting speed (V <sub>c</sub> ) m/min.	100-150	150-200	12-15
Feed (f) mm/U	0.2-0.4	0.05-0.2	0.05-0.3
Cutting depth (a <sub>p</sub> ) mm	2-4	0.05-2	0.5-3
Tools according ISO	P 10-P 20*	P 10*	-

\* Use wear resistant coated cemented carbide, e.g. Coromant 4015 or Seco TP 100.

### MILLING

#### FACE- AND EDGEMILLING

Cutting parameter	Milling with cemented carbide		HSS
	Medium turning	finish turning	
Cutting speed (V <sub>c</sub> ) m/min.	90-120	120-150	15
Feed (f) mm/U	0.2-0.3	0.1-0.2	0.1
Cutting depth (a <sub>p</sub> ) mm	2-4	1-2	1-2
Tools according ISO	K 15*	K 15*	-

\* Use wear resistant coated cemented carbide, e.g. Coromant 4015 or Seco TP 100.

#### END MILLING

Cutting parameter	Solid carbide	Milling cutter w. indexable tips	Coated HSS
Cutting speed (V <sub>c</sub> ) m/min.	45-55	90-110	12*
Feed (f) mm/U	0.01-0.20**	0.06-0.20**	0.01-0.30**
Tools according ISO	K 20	P 25***	-

\* for TiCN-coated end mills made of HSS V<sub>c</sub> ~ 25-30 m/min.

\*\* depends on radial depth of cut and on milling cutter - diameter

\*\*\* Use wear resistant coated cemented carbide, e.g. Coromant 3015 or SECO T15M.

### DRILLING

#### SPIRAL DRILL MADE OF HSS

Driller-φ mm	Cutting speed (V <sub>c</sub> ) m/min.	Feed (f) mm/U
0 - 5	5 - 8*	0.05-0.15
5 - 10	5 - 8*	0.15-0.25
10 - 15	5 - 8*	0.25-0.35
15 - 20	8 - 8*	0.35-0.40

\* for TiCN-coated end mills made of HSS V<sub>c</sub> ~ 25-30 m/min.

#### CARBIDE METAL DRILLER

Cutting parameter	Drill type Insert drill	solid carbide tip	Coolant bore driller with carbide tip*
Cutting speed (V <sub>c</sub> ) m/min.	80-110	40	35
Feed (f) mm/U	0.08-0.14**	0.10-0.15**	0.10-0.20**

\* driller with coolant bores and a soldered on carbide tip

\*\* depends on driller-diameter

### GRINDING

Grinding method	soft annealed	hardened
Surface grinding, straight grinding wheels	A 13 HV	B 107 R75 B3* 3SG 46 GVS** A 46 GV
Surface grinding	A 24 GV	3SG 36 HVS**
Cylindrical grinding	A 60JV	B 126 R75 B3* 3SG 60 KVS** A 60 IV
Internal grinding	A 46 JV	B 126 R75 B3* 3SG 80 KVS** A 60 HV
Profile grinding	A 100 LV	B 126 R100 B6* 5SG 80 KVS** A 120 JV

\* for these applications we recommend CBN-wheels

\*\* grinding wheel from the company Norton Co.

## Zapp Materials Engineering GmbH

### TOOLING ALLOYS

Zapp-Platz 1  
40880 Ratingen  
P.O. Box 10 18 62  
40838 Ratingen  
Germany  
Phone +49 2102 710-591  
Fax +49 2102 710-596  
toolingalloys@zapp.com

### SERVICE CENTER

Hochstraße 32  
59425 Unna  
Germany  
Phone +49 2304 79-511  
Fax +49 2304 79-7652  
www.zapp.com

Further information regarding our products and locations are available in our image brochure and under [www.zapp.com](http://www.zapp.com)

The illustrations, drawings, dimensional and weight data and other information included in these data sheets are intended only for the purposes of describing our products and represent non-binding average values. They do not constitute quality data, nor can they be used as the basis for any guarantee of quality or durability. The applications presented serve only as illustrations and can be construed neither as quality data nor as a guarantee in relation to the suitability of the material.

This cannot substitute for comprehensive consultation on the selection of our products and on their use in a specific application. The brochure is not subject to change control.

Last revision: December 2017